

Critical Current Peaks at $3B_\Phi$ in Superconductors with Columnar Defects: Recrystallizing the Interstitial Glass

M. E. Gallamore, G. E. D. McCormack, and T. P. Devereaux

Department of Physics, University of Waterloo, Waterloo, Ontario Canada N2L 3G1

(Dated: February 2, 2008)

The role of commensurability and the interplay of correlated disorder and interactions on vortex dynamics in the presence of columnar pins is studied via molecular dynamics simulations. Simulations of dynamics reveal substantial caging effects and a non-monotonic dependence of the critical current with enhancements near integer values of the matching field B_Φ and $3B_\Phi$ in agreement with experiments on the cuprates. We find qualitative differences in the phase diagram for small and large values of the matching field.

PACS numbers: 74.25.Qt, 75.40.Mg, 67.40.Yv, 67.40.-w

The rich phases of vortex matter in high temperature superconductors result from a complex interplay between disorder, interactions and fluctuations[1]. Understanding the physics of these competing effects has been a challenge which underlies the nature of various static and dynamic phases and transitions between them. Of particular interest is the role of columnar defects created by heavy ion radiation in forming more effectively pinned phases of interacting vortices. Extended or correlated disorder is much more effective at pinning vortices than uncorrelated (point-like) disorder and produces upward shifts of several tesla in the irreversibility lines and concomitantly larger critical currents.

The physics of 3D vortex pinning via correlated disorder can be approximately mapped onto the problem of interacting quantum bosons in the presence of uncorrelated disorder in 2D[2]. This has formed the basis for many computational studies via quantum Monte Carlo simulations of local repulsive bosons[3] and exact diagonalization studies[4]. Several pinned phases of vortex matter emerge as a function of B/B_Φ , where B_Φ is the equivalent matching field where the number of vortices equals the number of defects. For the case where the pins outnumber the vortices ($B < B_\Phi$), a Bose-glass phase is formed where vortices are localized onto columnar defects and possess an infinite tilt modulus for tilts away from columnar alignment. For equal numbers of vortices and defects ($B = B_\Phi$), an analog to a Mott insulating phase exists which possesses an infinite compression modulus[2]. The existence of the Bose-glass phase is well documented[1, 3], and evidence for the Mott phase has been found in recent magnetization relaxation measurements at low temperatures[5, 6]. For the case when the vortices outnumber the pins, ($B > B_\Phi$), the situation is much less clear. Recent work has suggested that vortices not accommodated to the columnar defects are caged by pinned vortices to form a weakly pinned “interstitial Bose” glass. It has been conjectured that the melting temperature T_m decreases rapidly as the density of interstitial vortices increases for large fields, and either extends smoothly into the Bose glass phase[2]

or shows a change in slope (kink) at $B = B_\Phi$ [7, 8]. Some experiments[9, 10, 11, 12] do not show substantial changes of the irreversibility line at B_Φ , while others show only a mild kink at B_Φ [5, 6, 13, 14, 15]. The change is even less significant for larger defect concentrations (larger B_Φ).

Moreover, interesting effects are seen as B further increases past B_Φ . In analogy with the presence of Mott lobes in the dual superconducting-insulator transition in 3D, one would expect different phases at commensurate values of vortex filling. Nowak *et al* found that the critical current in $\text{Ti}_2\text{Ba}_2\text{CuO}_{6+\delta}$ decreases for $B > B_\Phi$ but then increases and goes through a maximum near $3B_\Phi$ [6], which is currently unaddressed by theory.

One of the weakness of previous numerical studies[3, 4] is the use of a short-range screened interaction which misses the softening of the shear modulus in the absence of pins in the weak field limit as noted by Fetter, Hohenberg and Pincus[2, 16, 17]. The purpose of this paper is to address the importance of this omission by investigating the properties of the pinned and moving phases via 3D molecular dynamics simulations of vortices interacting via a long-range potential in the presence of columnar defects. Our key result is that the softening of the shear modulus in the low field limit has important implications for the phase diagram. We confirm the existence of a weakly pinned interstitial glass which becomes more weakly pinned as the field increases in agreement with previous studies of short-range interactions[4]. However we find a qualitatively new phase diagram for low fields where the interstitial glass melts near $B = B_\Phi$ and recrystallizes at higher fields when the matching field is below a critical value. In this regime we find strong numerical evidence for enhanced values of the critical current near three times the matching field. This questions the quantitative appropriateness of the mapping of vortex physics onto the physics of the superconductor-insulator transition without a properly detailed consideration of long-range interactions.

We model the motion of vortices as coupled pancakes on neighboring, continuous planes separated by a dis-

tance z , with the applied magnetic field aligned perpendicularly to the planes. The off-lattice simulation models the motion of vortices referenced by a 2D coordinate $\mathbf{r}$ under the influence of pinning and repulsive vortex interactions, and driving, line bending, and thermal forces:

$$m_l \ddot{\mathbf{r}}_i = -\eta_l \dot{\mathbf{r}}_i + \mathbf{f}_D + \mathbf{f}_T - \frac{\partial H(\{\mathbf{r}_1, \mathbf{r}_2 \dots\})}{\partial \mathbf{r}_i}. \quad (1)$$

Here $f_D = \Phi_0 J/c$ is the Lorentz force per unit length due to an applied current density J perpendicular to the magnetic field. $\eta_l = \frac{\Phi_0^2}{2\pi\xi^2\rho_n c^2}$ is the Bardeen-Stephen viscous drag coefficient, with $\Phi_0 = (hc/2e)$ the flux quantum and ρ_n the normal state resistivity. The Langevin thermal force per unit length f_T is normalized to set the rms vortex velocity via the equipartition theorem. The Hamiltonian H is the sum of the line tension for bending, and vortex-vortex and vortex-disorder potentials per unit length constructed via London theory. The line tension is given by $\epsilon_l = \epsilon \ln(\kappa)\epsilon_0$ with $\epsilon = (m_c/m_{ab})^2$, $\kappa = \lambda/\xi$, $\epsilon_0 = (\Phi_0/4\pi\lambda)^2$, and λ magnetic penetration depth. The vortex interaction is given by a sum of pairwise interactions $V_{v-v}(\mathbf{r}) = \epsilon_0 K(\mathbf{r}/\lambda)$ with K a Hankel function[1]. We model the correlated extended defects as smooth parabolic traps of width R_p and uniform depth $V_p = \epsilon_l/4$. Defects are randomly placed and aligned along the c -axis.

For DC transport, in most cases the vortex mass per unit length m_l is overall quite small in comparison with the other parameters in Eq. (1)[18] and has thus usually been neglected in previous numerical studies in 3D of vortex dynamics[19]. However, in the case of superconductors near a Mott instability, such as the underdoped cuprates, the vortex mass can be immensely enhanced as the system approaches a superconductor-insulator transition[20]. We thus keep this term and simply relate the vortex mass to the mass of the highly renormalized electrons confined to the vortex core region, $m_l = m_{eff} n \pi \xi^2$, with n the electron density and m_{eff} the in-plane effective mass of the electron renormalized by strong interactions. While we have found that the vortex mass has an impact on the magnitude of the critical current, the relative J_c for different vortex densities do not drastically depend on the choices made.

Periodic boundary conditions are imposed in the planes to maintain constant global flux density, and open boundary conditions are employed along the c -axis. Temperature is chosen which is high enough to allow individual vortices to be quickly accommodated to defects in the absence of a driving current but well below the glass temperature[4].

We measure all energies in units of the bare line bending energy ϵ_0 and measure all lengths in units of $d = 4\xi$. A natural time unit t_0 is chosen to be $\pi\kappa\eta_l d^2/\epsilon_l$ and the time step is further discretized in units of $0.01t_0$ for the simulations. The current is measured in units of the BCS depairing current $J_0 = \Phi_0 c \kappa / 12\sqrt{3}\pi^2 \lambda^3$, and resis-

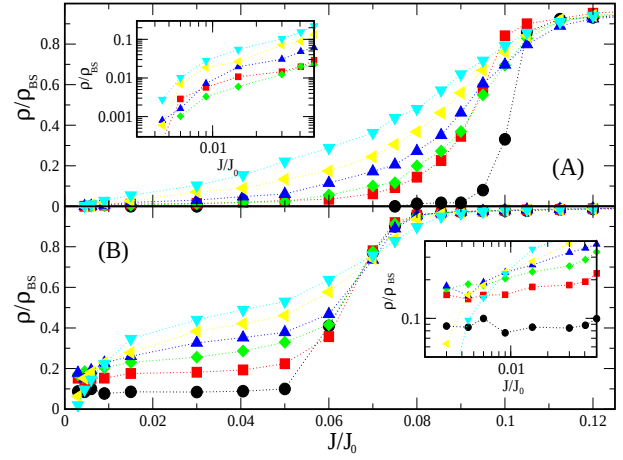


FIG. 1: Resistivity as a function of driving current for different values of the applied magnetic field referenced to the matching field B_Φ for $B_\Phi/H_{c2} \times 10^3 = 7.32$ (A) and 1.525 (B), respectively. The values of B/B_Φ are indicated as follows: Panel (A): 0.3 (circles), 0.8 (squares), 1 (diamonds), 1.25 (up triangles), 1.48 (left triangles), and 2 (down triangles); and Panel (B): 0.5 (circles), 1 (squares), 1.5 (diamonds), 2 (up triangles), 3 (left triangles), and 4 (down triangles). Solid lines are guides. The insets show the low current resistivities. Currents, resistivities are measured in units of J_0, ρ_{BS} respectively, as defined in the text. Color on-line.

tivities in terms of the Bardeen-Stephen flux-flow resistivity $\rho_{BS} = B\Phi_0/(c^2\eta_l)$. The other parameters used in the simulations are dictated by values appropriate for $\text{YBa}_2\text{Cu}_3\text{O}_7$: $m_{eff} = 5m_e$, $R_p = 2\xi$, $\xi = 17\text{\AA}$, $z = 12\text{\AA}$, $\kappa = 100$, and $\epsilon = 1/25$, giving $H_{c2} = 120\text{T}$.

Our simulations were performed using up to 40,000 vortex segments in a $128d \times 128d$ square periodic cell containing 80 planes, where finite size effects were investigated and found to be minimal. Measurements are taken over an interval of $10^6 t_0$ after the system has reached a steady state after a typical time $3 \times 10^5 t_0$. We typically average the results over several hundred realizations of disorder particularly at smaller driving forces. We measure the average vortex velocity in the direction of the Lorentz force corresponding to the voltage drop across the sample, and determine the resistivity $\rho = \mathcal{E}/J$.

Our results for the resistivity ρ versus the applied current density J are shown for a series of vortex densities below and above the matching field B_Φ for two different values of B_Φ in Fig. (1A and B). All error bars are equal to the symbol size. For the pinned Bose-glass regime $B < B_\Phi$ and for appreciable B_Φ (Fig. 1A), vortices are localized on separate columnar defects for small J until an abrupt transition to a moving regime ensues near $J \sim 0.1J_0$ where the vortices simultaneously become unpinned. For larger driving currents, vortices are in the flux flow regime and the resistivity approaches ρ_{BS} . The de-pinning transition occurs within a narrow range of currents corresponding to single vortex pinning. Conse-

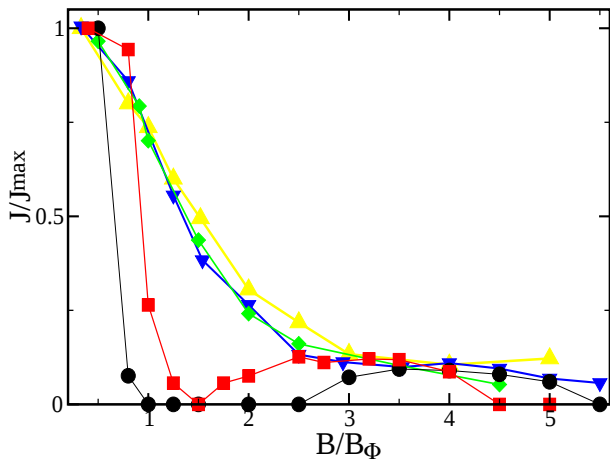


FIG. 2: Normalized critical currents as a function of B/B_Φ for different densities of columnar defects. The density of defects is given by $10^3 \times B_\Phi/H_{c2} = 1.525, 1.906, 3.05, 4.88$, and 7.32 for circles, squares, down triangles, diamonds, and up triangles, respectively. Color on-line.

quently, as B increases, the depinning transition occurs for smaller J and significantly broadens as the effective role of disorder diminishes relative to the vortex lattice interaction, in agreement with previous simulations[4]. The resistivity increases monotonically with increasing B as shown in the inset of Fig. (1A). For values of B near and above the matching field, a low-current tail develops for small J and continues to increase as more and more interstitial vortices are not able to reside on columnar defects due to the repulsion from the pinned vortices. These interstitial vortices are caged by the pinned vortices forming an weakly pinned interstitial glass with a much reduced critical current J_c , as suggested in Refs. [7, 8]. As B is further increased, the interstitial glass melts into a interstitial liquid where channels of vortices flow around pinned vortices for arbitrarily small J and give a resistivity proportional to the fraction of interstitial to pinned vortices. We note that for our parameter choices we do not observe a Mott insulating phase as we always have interstitial vortices for $B/B_\Phi = 1$ due to the long-range vortex repulsion and high temperatures.

Important differences however are observed for smaller values of B_Φ (Fig. 1B). For $B < B_\Phi$ in this case, the transition to depinning occurs at lower J and is substantially broadened compared to Fig. (1A). A non-monotonic dependence of the resistivity appears as shown in the inset of Fig. (1B). For low driving forces the resistivity rises with increasing B for $B/B_\Phi < 1.5$ and becomes greater than $0.1\rho_{BS}$ for $B > B_\Phi$ as the interstitial glass melts into an interstitial liquid as the density of vortices is increased. However at larger fields the resistivity decreases and becomes less than $0.1\rho_{BS}$ for fields near three times the matching field. *This indicates that for low B_Φ the Bose glass melts into an interstitial liquid near the*

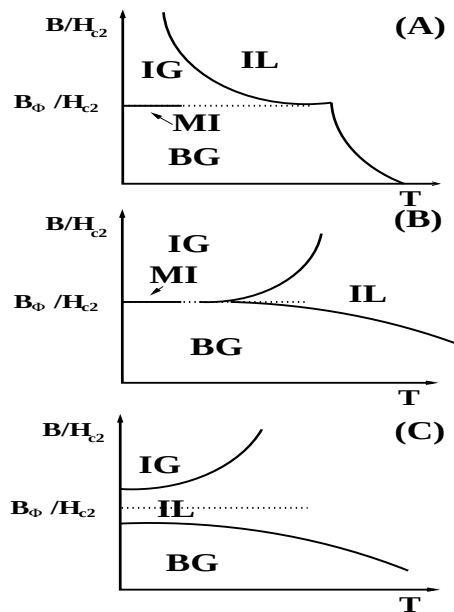


FIG. 3: Conjectured phase diagram for large (A), intermediate (B), and small (C) matching field densities.

matching field and recrystallizes into an interstitial glass at larger values of B/B_Φ , in contradiction to the phase diagram proposed previously[7].

We can make this more quantitative by defining a critical current density J_c as the value of the current density corresponding to a resistivity of 10% of ρ_{BS} . For a number of different molecular dynamics runs of different B_Φ , the values we obtain for J_c are shown in Fig. (2) as a function of B/B_Φ normalized to the values of J_c determined in the small B/B_Φ limit. For large B_Φ , the critical current decreases monotonically with B/B_Φ with a gradual fall-off near the matching field. For smaller values of B_Φ the fall-off near B_Φ becomes much more abrupt, suggesting that a magnitude of the kink in the melting curve would be dependent on the value of B_Φ , reconciling previous experiments[5, 6, 9, 10, 11, 12, 13, 14, 15]. For even smaller B_Φ , the fall-off is dramatic and the interstitial glass weakens appreciably and melts ($J_c = 0$) near a critical value of $B_\Phi^c/H_{c2} \sim 1.9 \times 10^{-3}$. Remarkably, the critical current resurrounds for larger values of the magnetic field and has a broad peak near $B = 3B_\Phi$ for $B_\Phi/H_{c2} \times 10^3 = 1.906$ before falling off again at still larger fields. This reproduces the peak near three times the matching field seen in experiments on $Tl_2Ba_2CuO_{6+\delta}$ [6]. However we see that still smaller values of B_Φ yields a critical current peak at larger values of B/B_Φ suggesting that this peak would be dependent on the number of defects. While we expect that the actual value of the critical field B^c might depend on our choice of defining J_c , we do not expect the reentrant behavior into the interstitial glass to be qualitatively changed. A proposed phase diagram which encompasses our results for different B_Φ

is given in Figure (3).

Using renormalization group arguments it was shown by Nelson and Seung that for clean systems the interactions between vortex lines are renormalized to zero near H_{c1} and leads to the melting of the Abrikosov lattice as $H \rightarrow H_{c1}$ [17]. Thus we might expect that the melting of the interstitial glass for $B - B_\Phi \geq 0^+$ is similar to the melting of the vortex lattice near H_{c1} [2, 17]. However for $B < B_\Phi$ vortex localization onto unoccupied columnar defects helps to reduce vortex fluctuations and one might expect the Bose glass to be stable near H_{c1} as vortices occupy the strongest defects. Yet once $B > B_\Phi$ the interstitial vortices feel a much reduced and screened defect interaction and suffer the downward renormalization of the shear modulus as in clean systems. This is borne out in our simulations for small defect concentrations. As the field increases our simulations indicate that the interstitial glass recrystallizes. This can be viewed as a hardening of the shear modulus for increasing fields as the role of interactions increases.

What leads to the recrystallization of the melted interstitials at larger values of B for small defect concentrations? At large vortex concentrations the Coulomb potential is effectively short-range due to screening and the effects of disorder are also screened by flux line collisions, and indeed our results are consistent with prior simulations for contact repulsive potentials[4]. The system favors forming dislocations at larger fields and the domains are vortices are easily depinned. For smaller vortex concentrations, new physics arises as screening is no longer effective and the bare long-range repulsive forces encourage longer-range ordering concomitant with decreased prevalence of dislocation and subsequent enhanced vortex pinning.

To check these ideas, we plot in Figure (4) time-averaged structure plots for $B = 3B_\Phi$ at two values of B_Φ . While long-range order is not seen even on the length scale of our simulations, it is clear that orientational short-range order is more prevalent for the small B_Φ results than the large ones, with subsidiary structure peaks at the reciprocal lattice vectors up to $1/2$ the height of the central ($Q = 0$) peak. When averaged over many disorder configurations, the orientational order is lost for both values of B_Φ , yet it is clear that the effective range of the vortex repulsion is longer for smaller B_Φ . We would expect that for still smaller values of B_Φ positional order would grow for systems of fixed finite size L with the possible formation of Bragg-like peaks. Most likely the positional order would not be quantitatively relevant for $L \rightarrow \infty$.

In summary, we have presented numerical simulations of interacting vortex dynamics in the presence of columnar disorder as a function of B/B_Φ and B_Φ/H_{c2} . We find a monotonic decrease in the critical current for large values of B_Φ , with a sharp drop-off near the matching field, consistent with prior notions of the weakly pinned inter-

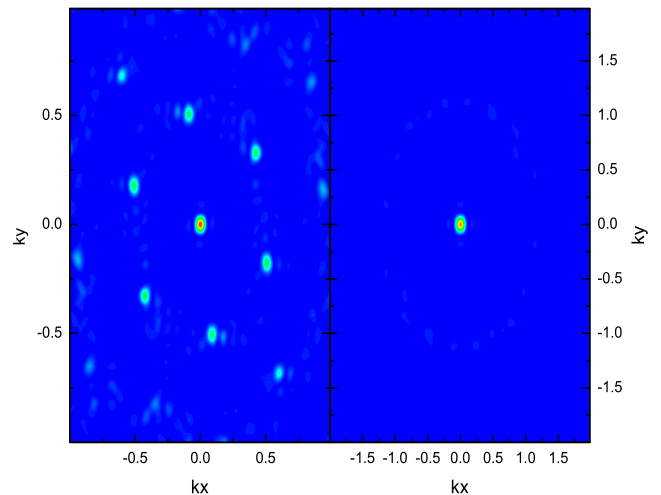


FIG. 4: Structure factor in the pinned phase at three times the matching field $B/B_\Phi = 3$ for $10^3 \times B_\Phi/H_{c2} = 1.525$ (left) and 7.32 (right) panels, respectively. Momentum is measured in units of $1/d$. Color on-line.

sitial glass emerging at higher fields. For smaller values of B_Φ however, we see abrupt melting at $B = B_\Phi$ and recrystallization near $B = 3B_\Phi$ of the interstitial glass, suggesting modifications to the phase diagram due to the role of long-range interactions even for columnar disorder.

T.P.D. would like to thank T. Giamarchi, M. J. P. Gingras, and T. F. Rosenbaum for many useful discussions. T.P.D. would like to acknowledge support from NSERC, PREA, Canadian Foundation for Innovation, the Ontario Innovation Trust, and the Alexander von Humboldt foundation.

-
- [1] G. Blatter *et al.*, Rev. Mod. Phys. **66**, 1125 (1994).
 - [2] D. Nelson, Phys. Rev. Lett. **60**, 1973 (1988); D. Nelson and V. M. Vinokur, Phys. Rev. Lett. **68**, 2398 (1992); Phys. Rev. B **48**, 13060 (1993).
 - [3] R.T. Scalettar, G. Batrouni, and G.T. Zimanyi, Phys. Rev. Lett. **66**, 3144 (1991); N. Trivedi, D. Ceperley, and W. Krauth, Phys. Rev. Lett. **67**, 2307 (1991); W. Krauth and N. Trivedi, Europhys. Lett. **14**, 627 (1991); K. Bernardet, G. G. Batrouni, J.-L. Meunier, G. Schmid, M. Troyer, and A. Dorneich, Phys. Rev. B **65**, 104519 (2002); P. Sen, N. Trivedi, and D.M. Ceperley, Phys. Rev. Lett. **86**, 4092 (2001).
 - [4] A. Nandgaonkar *et al.*, Phys. Rev. B **66**, 104527 (2002).
 - [5] K. M. Beauchamp *et al.*, Phys. Rev. Lett. **75**, 3942 (1995).
 - [6] E. R. Nowak *et al.*, Phys. Rev. B **54**, 12 725 (1996).
 - [7] L. Radzihovsky, Phys. Rev. Lett. **74**, 4923 (1995).
 - [8] A. I. Larkin and V. M. Vinokur, Phys. Rev. Lett. **75**, 4666 (1995).
 - [9] T. K. Worthington *et al.*, Phys. Rev. B **46**, 11854 (1992).

- [10] L. Krusin-Elbaum *et al.*, Phys. Rev. Lett. **72**, 1914 (1994).
- [11] G. Nakielski *et al.*, Phys. Rev. Lett. **76**, 2567 (1996).
- [12] A. V. Samoilov, *et al.* Phys. Rev. Lett. **76**, 2798 (1996).
- [13] A. Mazilu *et al.*, Phys. Rev. B **58**, 8909 (1998).
- [14] A. W. Smith *et al.*, Phys. Rev. B **59**, 11 665 (1999).
- [15] A. W. Smith *et al.*, Phys. Rev. Lett. **84**, 4974 (2000); *ibid.*, Phys. Rev. B **63**, 64514 (2001).
- [16] A. L. Fetter, P. C. Hohenberg, and P. Pincus, Phys. Rev. **147**, 140 (1966).
- [17] D. R. Nelson and S. Seung, Phys. Rev. B **39**, 9153 (1989).
- [18] H. Suhl, Phys. Rev. Lett. **14**, 226 (1965); G. Baym and E. Chandler, J. Low Temp. Phys. **50**, 57 (1983); M .W. Coffey and J. R. Clem, Phys. Rev. B **44**, 6903 (1991); D. M. Gaitonde and T. V. Ramakrishnan, **56**, 11951 (1997); E. B. Sonin *et al.*, **57**, 575 (1998); G. E. Volovik, JETP Lett. **67**, 528 (1998); N. B. Kopnin and V. M. Vinokur, Phys. Rev. Lett. **81**, 3952 (1998).
- [19] A. van Otterlo *et al.*, Phys. Rev. Lett. **81**, 1497 (1998); C. Olson *et al.*, Phys. Rev. Lett. **85**, 5416 (2000).
- [20] S. Doniach and M. Inui, Phys. Rev. B **41**, 6668 (1990). Recent studies of vortex dynamics in YBaCu₂O_{7+ δ} thin film microbridges [M. V. Pedyash *et al.*, IEEE Trans. of App. Supercond. **5**, 1387 (1995)] find a value of η two orders of magnitude smaller than the Bardeen-Stephen value using parameters appropriate for this material.